



H. J. Pam
Associate Professor,
Department of Civil
Engineering, The University
of Hong Kong



A. K. H. Kwan
Senior Lecturer,
Department of Civil
Engineering, The University
of Hong Kong



M. S. Islam
Research Associate,
Department of Civil and
Material Engineering,
University of Illinois at Chicago



Flexural strength and ductility of reinforced normal- and high-strength concrete beams

H. J. Pam, A. K. H. Kwan and M. S. Islam

A number of singly reinforced concrete beams made of normal- and high-strength concretes were tested under monotonically increasing loads to study their flexural behaviour and to compare the flexural ductility of normal- and high-strength concrete beams. The flexural strength results verified that British Standard BS 8110, after modification as per the recommendation of The Concrete Society Technical Report 49, is reasonably accurate for application to high-strength concrete beams. On the other hand, the flexural ductility results revealed that the major structural parameters determining the ductility of singly reinforced beams are: (1) for given materials, the tension steel ratio; and (2) in more general cases, the tension steel to balanced steel ratio and the concrete grade. Based on the available test results, a simple formula for predicting the ductility of normal- and high-strength concrete beams is developed. Lastly, in order to avoid brittle failure, it is proposed to set a maximum limit to the tension steel to balanced steel ratio, whose values at different concrete strengths are given in the paper.

NOTATION

A_s	tension steel area
A_{sb}	balanced steel area, i.e. tension steel area that will lead to balanced failure
b	breadth
d	effective depth to tension reinforcement
d_n	depth to neutral axis
f_c	uniaxial compressive strength of concrete
f_{cu}	cube compressive strength of concrete
f_s	axial stress developed in tension reinforcement
f_y	yield stress of tension reinforcement
M_p	experimentally measured bending strength
M_u	theoretically evaluated bending strength
α	parameter of equivalent stress block defining the depth of stress block
β	parameter of equivalent stress block defining the average stress
Δ	deformation
Δ_{max}	maximum deformation at failure
Δ_y	deformation when the member yields
ϵ_c	concrete strain at extreme fibre
ϵ_{cu}	ultimate concrete strain, i.e. value of ϵ_c at peak bending moment

ϵ_s	axial strain developed in tension reinforcement
ϵ_y	yield strain of tension reinforcement
μ	ductility factor defined by equation (1)
ρ	tension steel ratio, i.e. $A_s/(bd)$
ρ_b	balanced steel ratio, i.e. tension steel ratio that will lead to balanced failure

I. INTRODUCTION

With the rapid advancement of concrete technology, high-strength concrete is being more widely used in reinforced concrete buildings. Many countries around the world have now raised the upper limit of the concrete strength in their building codes^{1,2} to take into account the higher strength of modern concrete. However, several aspects of the material behaviour of high-strength concrete differ significantly from those of normal-strength concrete and therefore high-strength concrete should not just be regarded as normal concrete with higher strength. For instance, the Young's modulus, tensile strength and shear strength of concrete do not increase in direct proportion to the compressive strength.^{3,4} Hence, in the design of reinforced concrete structures incorporating high-strength concrete, more careful checking of the rigidity, cracking and shear strength of the structures is needed.

Perhaps of greater concern is the generally higher brittleness of high-strength concrete compared to that of normal-strength concrete.^{3,4} High-strength concrete is more brittle in nature because cracks in this material do not always follow the aggregate-hardened cement paste interfaces due to the improved interfacial bond strength of high-strength concrete but may cut right through the hardened cement paste and even the aggregate particles leading to rapid propagation of the cracks and sudden or sometimes explosive failure of the concrete. Because of this problem, many structural engineers hesitate in using high-strength concrete, despite its obvious advantages.

However, the ductility of a reinforced concrete member is not the same as that of the constituting concrete. One common misunderstanding about the ductility of members made of high-strength concrete is the thinking that the ductility of a member made of high-strength concrete is always lower than that of a similar member made of normal-strength concrete. In fact, the ductility of a member is dependent on the type of

member, the loading arrangement and the reinforcement layout as well as the ductility of the materials used. Detailed ductility evaluation is needed before it is known whether a member made of high-strength concrete has a higher or lower ductility than a similar member made of normal-strength concrete.

In the case of a reinforced concrete column, the major parameters determining its ductility include the axial load ratio, the amount of longitudinal reinforcement, the amount of confining reinforcement and of course the ductility of the concrete used.^{5,6} It is true that for a given column subjected to a prescribed axial load ratio, the use of high-strength concrete in place of normal-strength concrete will significantly reduce the ductility of the column. Nevertheless, the loss in ductility due to the use of high-strength concrete can be replenished by increasing the amount of confining reinforcement. This will put the concrete core under greater confining pressure and substantially increase the ductility of the concrete column. In addition, if necessary, since the axial load capacity is increased, the axial load ratio may be slightly reduced to further improve the ductility of the column. Thus, provided the column to be made of high-strength concrete is properly designed, its ductility can be restored to at least the level of a similar column made of normal-strength concrete.

In the case of a reinforced concrete beam, the major parameters determining its ductility include the amount of tension reinforcement, the amount of compression reinforcement, and the strength and ductility of the materials used.⁷⁻⁹ Depending on the amount of reinforcement provided, the tension reinforcement may or may not yield before the concrete in the compression zone is crushed. If the amount of tension reinforcement is small, the tension reinforcement will yield before the concrete is crushed and the beam will fail in a ductile manner. If the amount of tension reinforcement is large, the concrete will be crushed without prior yielding of the tension reinforcement and the beam will fail in a brittle manner. The type of concrete used has, of course, certain effects on the ductility of the beam. When high-strength concrete is used, the concrete will have higher strength but lower ductility. At fixed amounts of tension and compression reinforcement, an increase in concrete strength will reduce the neutral axis depth and increase the strain that will be reached by the tension reinforcement when the concrete is crushed leading to an increase in ductility of the beam. On the other hand, the lower ductility of the concrete does adversely affect the ductility of the beam. Hence, the higher strength and lower ductility of high-strength concrete have opposite effects and the use of high-strength concrete does not necessarily increase or decrease the ductility of the beam. Detailed analysis is needed to evaluate the net effect on the ductility of the beam.

Although the stiffness and strength of reinforced concrete members have been thoroughly studied, there has been relatively little research on the ductility of reinforced concrete members especially those made of high-strength concrete. Herein, a research project aiming to study the ductility of reinforced concrete beams made of normal- and high-strength concretes is presented. In the project, by testing beams with different amounts of longitudinal reinforcement provided and cast from different grades of concrete, the effects of reinforce-

ment content and concrete grade on the ductility of reinforced concrete beams were investigated. It is hoped that the results will be useful for practising engineers in predicting and controlling the ductility of reinforced concrete beams.

2. DUCTILITY FACTOR

The term 'ductility' is defined as the ability of the material/member to sustain deformation beyond the elastic limit while maintaining a reasonable load carrying capacity until total failure. Depending on the type of material or member being referred to, the deformation employed to evaluate ductility may be strain, curvature, displacement or rotation. In the particular case of a reinforced concrete beam, the deformation most suited for this purpose is the curvature of the beam. As an alternative, the deflection of the beam, which is generally easier to measure, may also be used. When evaluating ductility, the most important parameter to be considered is the maximum deformation that the material/member can sustain prior to failure. However, two different materials or members having a similar magnitude of maximum deformation at failure can have different stress-strain or load-deflection behaviours and therefore different ductility. For this reason, it is better to express the ductility in terms of a dimensionless ductility factor, μ , as defined below

$$\mu = \frac{\Delta_{\max}}{\Delta_y}$$

where Δ_{\max} is the maximum deformation at failure and Δ_y is the deformation when the material or member yields.

The determination of Δ_y can pose difficulties because the load-deformation curve may not have a well-defined yield point at all. Absence of a well-defined yield point may occur, in the case of a reinforced concrete beam, due to the tension reinforcement at different beam depths reaching yield strain at different times, and in the case of a building frame, due to the plastic hinges in different parts of the structure forming at different load levels. The existing methods used to estimate Δ_y have been summarised by Park.¹⁰ Among these, the most practicable and realistic estimation of Δ_y is the one obtained from an equivalent elasto-plastic system with its equivalent elastic stiffness taken as the secant stiffness at 75% of the ultimate load of the real system, as shown in Fig. 1. The secant stiffness at a load level significantly higher than the usual cracking load is used instead of the initial elastic stiffness in order to account for the reduction in stiffness due to cracking. This method of determining Δ_y is adopted in the present study. From Fig. 1, it can be seen that the value of Δ_y so evaluated is actually equal to 4/3 times the value of Δ at 75% of the ultimate load.

The maximum deformation at failure, Δ_{\max} , is dependent on how the failure point is defined because failure is actually a process during which the deformation of the material/member keeps on increasing. Several different definitions have been used to establish a threshold point of failure.¹⁰ The definition adopted here is the point on the descending part of the load-deformation curve where the load has dropped to 85% of the maximum load applied (see Fig. 1). This definition has the advantages that it can be applied to basically all kinds of

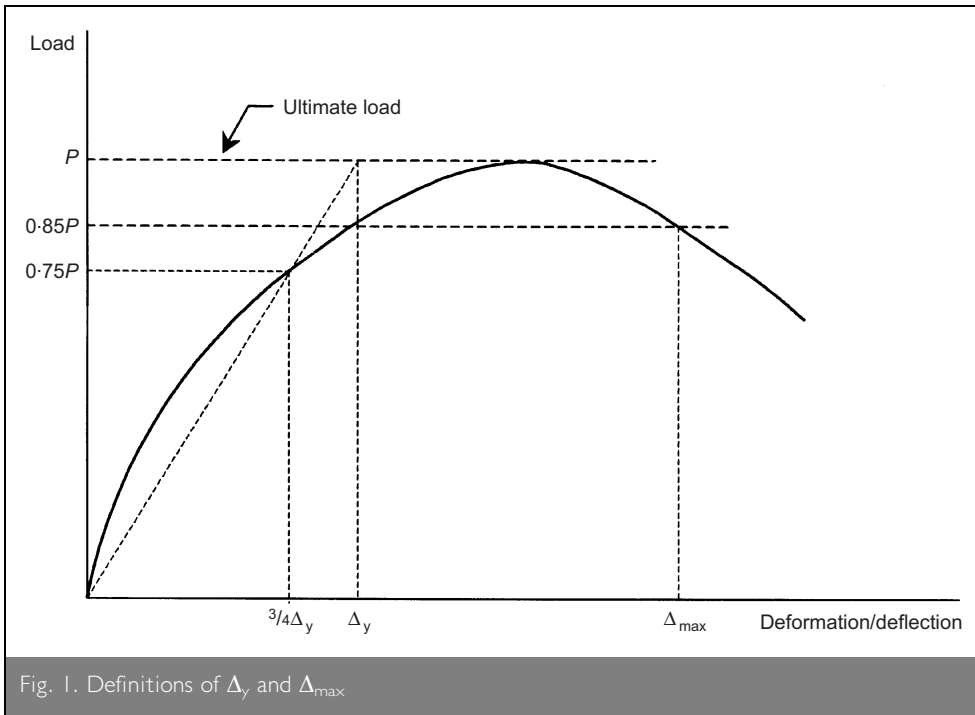


Fig. 1. Definitions of Δ_y and Δ_{max}

structures and is relatively easy to determine either analytically or experimentally. Having taken into account the ability of the material/member to deform beyond the peak load, it is regarded as a much better measure of ductility than most other definitions.

3. FLEXURAL BEHAVIOUR OF REINFORCED CONCRETE BEAMS

The theoretical ultimate moment of a singly reinforced concrete beam may be calculated using an equivalent rectangular stress block for the concrete as illustrated in Fig. 2. Axial load equilibrium gives

$$2 \quad A_s f_s = \alpha \beta f_c b d_n$$

where A_s is the area of tension reinforcement, f_s is the axial stress developed in the tension reinforcement, f_c is the compressive strength of the concrete, b is the breadth of the beam, d_n is the neutral axis depth, and α and β are the coefficients defining the depth and average stress of the equivalent

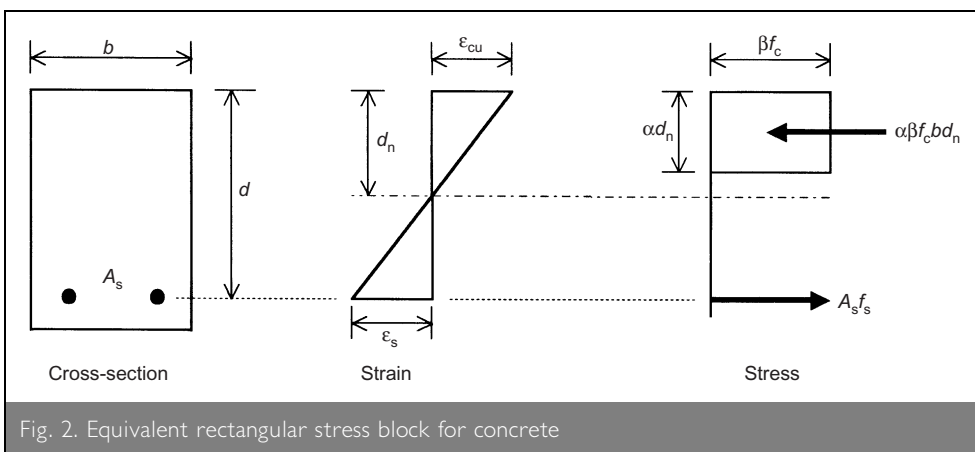


Fig. 2. Equivalent rectangular stress block for concrete

rectangular stress block. From this equation, the neutral axis depth may be determined as

$$3 \quad d_n = \frac{A_s f_s}{\alpha \beta f_c b}$$

Having determined the neutral axis depth, the ultimate moment may be evaluated as

$$4 \quad M_u = \alpha \beta f_c b d_n (d - 0.5 \alpha d_n)$$

in which M_u is the ultimate moment and d is the effective depth of the beam.

Depending on the strain reached by the tension reinforcement when the concrete in the compression zone is crushed, the beam may fail with or without prior

yielding of the tension reinforcement. Assuming plane sections remain plane when the beam is subjected to bending, the axial strain is proportional to the distance from the neutral axis, as shown in Fig. 2. When the concrete strain at the extreme compressive fibre, ϵ_c , reaches the ultimate concrete strain, ϵ_{cu} (ϵ_{cu} is the corresponding value of ϵ_c when the beam section delivers greatest moment of resistance), the strain of the tension reinforcement, ϵ_s , reaches the following value

$$5 \quad \epsilon_s = \frac{d - d_n}{d_n} \epsilon_{cu}$$

Denoting the yield strain of the tension reinforcement by ϵ_y and comparing the above value of ϵ_s to ϵ_y , the failure mode of the beam can be determined as follows: If ϵ_s is greater than ϵ_y , the tension reinforcement will yield before the concrete is crushed (tension failure). If ϵ_s is smaller than ϵ_y , the concrete will be crushed without prior yielding of the tension reinforcement (compression failure). If ϵ_s is equal to ϵ_y , the tension reinforcement will yield at the same time when the concrete is crushed (balanced failure). From equation (5), the condition for balanced failure is obtained as

$$6 \quad \frac{d_n}{d} = \frac{\epsilon_{cu}}{\epsilon_{cu} + \epsilon_y}$$

Using equation (2), the amount of tension reinforcement that will lead to balanced failure, A_{sb} , may be determined as

$$7 \quad A_{sb} = \alpha \beta \frac{f_c}{f_y} \frac{\epsilon_{cu}}{\epsilon_{cu} + \epsilon_y} b d$$

in which f_y is the yield stress of the tension reinforcement. Expressing the area of tension reinforcement in

dimensionless form as a tension steel ratio, ρ , defined by $\rho = A_s/(bd)$, the balanced steel ratio, ρ_b , i.e. the tension steel ratio that will lead to balanced failure, can be obtained as

$$\rho_b = \alpha \beta \frac{f_c}{f_y} \frac{\epsilon_{cu}}{\epsilon_{cu} + \epsilon_y}$$

If ρ is less than ρ_b (under-reinforced), the tension reinforcement will yield before the concrete is crushed and the beam will fail in a ductile manner. If ρ is greater than ρ_b (over-reinforced), the tension reinforcement will not yield even when the concrete is crushed and the beam will fail in a brittle manner.

4. PARAMETERS OF CONCRETE STRESS BLOCK

The compressive stress-strain curve of high-strength concrete differs quite significantly from that of normal-strength concrete.^{3,4} Relatively, the compressive stress-strain curve of high-strength concrete has the following characteristics

- (a) the ascending part is more linear
- (b) the strain at peak stress is larger
- (c) the descending part is steeper
- (d) the ultimate strain is smaller.

Thus, the rectangular stress block designed for normal-strength concrete should not be used indiscriminately for high-strength concrete. Without going into too much sophistication, it is suggested to follow the recommendation of The Concrete Society as given in its Technical Report 49.¹¹ According to the recommendation of The Concrete Society, the parabolic-rectangular stress-strain curve given in British Standard BS 8110,¹² which was originally developed for normal-strength concrete, may be used for high-strength concrete provided the ultimate concrete strain, ϵ_{cu} , is modified as shown below

9a	when $f_{cu} \leq 60$ MPa, $\epsilon_{cu} = 0.0035$
9b	when $f_{cu} > 60$ MPa, $\epsilon_{cu} = 0.0035 - (f_{cu} - 60)/50000$

The stress block given in BS 8110 consists of two portions, a parabolic portion and a rectangular portion. It is converted to an equivalent rectangular stress block as shown in Fig. 2 before being applied to the analysis in the present study. Considering the equilibrium conditions, the values of α and β defining the depth and average stress of the equivalent rectangular stress block for different concrete strengths are evaluated and the results are presented in

f_{cu} : MPa	ϵ_{cu}	α	β	Balanced steel ratio, ρ_b : %	
				$f_y = 250$ MPa	$f_y = 460$ MPa
40	0.0035	0.867	0.986	6.75	3.00
50	0.0035	0.854	0.981	8.27	3.68
60	0.0035	0.842	0.977	9.75	4.34
70	0.0033	0.823	0.968	10.84	4.78
80	0.0031	0.804	0.956	11.75	5.14
90	0.0029	0.784	0.941	12.44	5.40
100	0.0027	0.766	0.919	12.90	5.54

Table 1. Parameters of the concrete stress block and balanced steel ratios

Table 1. Having evaluated the values of ϵ_{cu} , α and β , the balanced steel ratios for different concrete strengths and different types of tension reinforcement are calculated using equation (8) and are listed in columns 5 and 6 of Table 1. It can be seen from the results tabulated in Table 1 that as the concrete strength increases, the balanced steel ratio also increases.

5. TESTING PROGRAMME

Twenty rectangular singly reinforced concrete beams having dimensions 200 mm \times 300 mm \times 3000 mm (breadth \times depth \times length) were fabricated for testing. The beams were cast from normal- or high-strength concrete with cube compressive strength ranging from 35 to 100 MPa. In order to study the effects of different amounts of reinforcement, the main reinforcement provided was varied from 0.8 to 5.5% of the effective beam section area. All the main reinforcement bars used were high-yield steel bars with yield strength within 520 to 580 MPa. The main bars were placed near the bottom of the beams. Near the top of the beams, two 12 mm diameter bars were added as hanger bars for fixing the stirrups. At the ends of the main bars, generous anchorage in the form of 90° hooks was provided to prevent bond-slip of the reinforcement bars. The stirrups added, which served as shear reinforcement, were designed such that the beams would fail only in bending, not in shear. All of the beams were simply supported at a span of 2600 mm and were tested by subjecting them to two monotonically applied point loads near mid-span, as illustrated in Fig. 3. Detailed properties of the beams are given in Table 2.

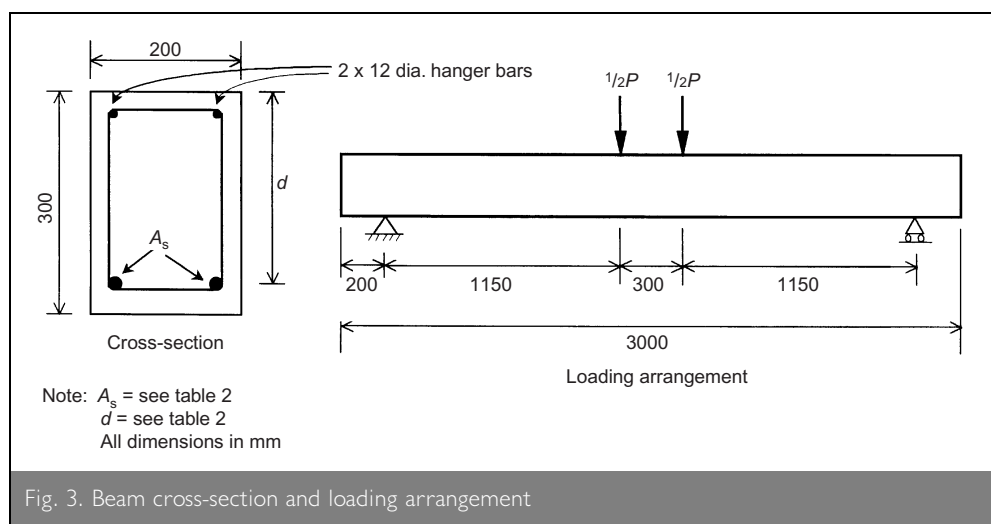


Fig. 3. Beam cross-section and loading arrangement

Beam no.	f_{cu} : MPa	d : mm	Main reinforcement		
			Layout	A_s : mm ²	f_y : MPa
1	37.4	264	2T16	402	579
2	36.8	264	3T16	603	579
3	36.4	260	2T25	982	578
4	42.3	260	2T25	982	536
5	46.4	260	2T25 + 1T16	1183	546
6	43.2	260	3T25	1473	536
7	58.6	260	2T25 + 1T20	1296	520
8	57.1	260	3T25	1473	520
9	58.6	256	2T32 + 1T16	1809	520
10	50.3	256	2T32 + 1T25	2099	519
11	58.8	256	2T32 + 1T25	2099	519
12	52.9	256	3T32	2414	519
13	58.8	256	3T32 + 2T16	2815	520
14	95.5	260	2T25	982	578
15	98.0	260	3T25	1473	578
16	102.5	260	3T25	1473	578
17	87.0	256	2T32	1608	546
18	90.3	256	3T32	2414	574
19	91.7	256	3T32	2414	574
20	83.5	256	3T32 + 2T16	2815	553

Table 2. Properties of the beam specimens. (Note: T denotes high-yield steel bar. The number before T is the number of bars and the number after T is the diameter of the bar in mm)

The loads were applied using a 500 kN computer controlled hydraulic actuator manufactured by MTS. During loading, the vertical deflections at mid-span of the beams were measured by a displacement transducer. The strains in the main reinforcement bars were measured by electrical resistance strain gauges glued at the location where maximum bending moment was expected. Visual inspection of the cracks was carried out throughout the tests and the crack patterns were recorded by a video camera. At the initial stage, the test was conducted using load control up to 75% of the theoretical ultimate load. Subsequently, the test was conducted using displacement control in order to capture the post-peak behaviour of the beam specimen. The test was terminated when the specimen failed completely, i.e. when the resistance of the specimen dropped to less than 85% of the measured ultimate load.

6. EXPERIMENTAL RESULTS

In terms of tension steel content, the beam specimens can be divided into three groups: under-reinforced beams, balanced-reinforced beams and over-reinforced beams. The different groups of beams were found to behave similarly at the elastic stage but quite differently during failure. In all the beams, fine vertical tension cracks started to appear near the mid-span region when the applied load reached about 50 to 60% of the ultimate load. Upon further loading, the flexural cracks developed in length and width, as well as increased in number. At the same time, some inclined cracks occurred between the support and the point of load application, i.e. within the region of bending moment and shear interaction. For the under-reinforced beams, regardless of the grade of the concrete used, extensive tension cracks were formed before peak load was reached. Failure of these beams was gradual and smooth, and was accompanied by fairly large deflection. For the over-reinforced beams, particularly those made of high-strength concrete, there were generally fewer number of tension cracks.

Their failure was more abrupt and sometimes even quite explosive due to brittle failure of the concrete without prior yielding of the tension reinforcement. The balanced-reinforced beams behaved in an intermediate manner between those of under-reinforced and over-reinforced beams, but generally they appeared to fail in a fairly brittle manner.

Due to the practical difficulty of accurate curvature measurement, the curvatures of the beams were not measured and only the deflections of the beams were obtained. Hence, instead of moment-curvature curves, the deformation behaviour of the beam specimens was studied in terms of moment-deflection curves. Some typical moment-deflection

curves (those of beams no. 2, no. 8 and no. 20) obtained from the tests are shown in Fig. 4. Beam no. 2, which was cast from concrete with relatively low cube strength ($f_{cu} = 36.8$ MPa) and was under-reinforced ($\rho/\rho_b = 0.57$), exhibited a fairly ductile moment-deflection behaviour. Beam no. 8, which was made of normal-strength concrete ($f_{cu} = 57.1$ MPa) and was provided with nearly balanced reinforcement ($\rho/\rho_b = 0.82$), exhibited a somewhat less ductile behaviour. On the other hand, beam no. 20, which was cast from high-strength concrete ($f_{cu} = 83.5$ MPa) and was over-reinforced ($\rho/\rho_b = 1.37$), failed in a rather brittle manner. It is thus evident that both the concrete grade and the ρ/ρ_b ratio have certain effects on the flexural ductility of reinforced concrete beams.

From the load measurement results and the moment-deflection curves of the beam specimens, the ultimate moment, M_p , and ductility factor, μ , of each specimen can be obtained. These

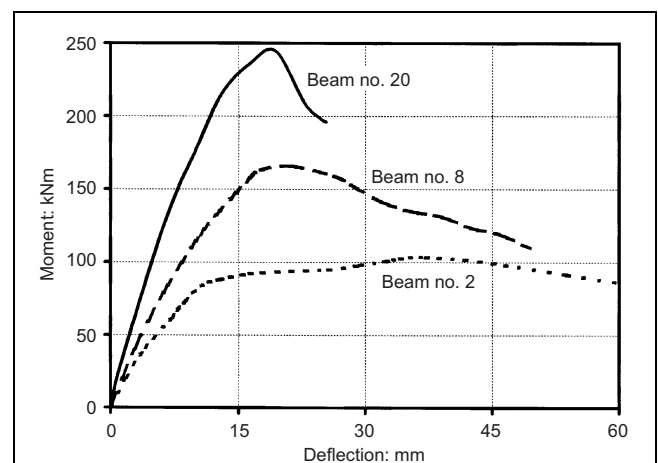


Fig. 4. Typical moment-deflection curves

results, together with the tension steel ratio, ρ , balanced steel ratio, ρ_b , tensile steel to balanced steel ratio, ρ/ρ_b , and the theoretically evaluated values of ultimate strength, M_u , are presented in Table 3 and analysed next.

6.1. Flexural strength analysis

In the present study, the theoretical ultimate moment, M_u , is evaluated using the parabolic–rectangular stress–strain curve given in British Standard BS 8110¹² and the recommended formula for ϵ_{cu} given in The Concrete Society Technical Report 49.¹¹ The experimental values of ultimate moment, M_p , are compared to the corresponding theoretical values M_u in terms of M_p/M_u ratios, which are listed in Table 3. It is seen that the M_p/M_u ratios for beams with $f_{cu} \approx 37$ MPa are around 1.11 to 1.39, those for beams with $f_{cu} \approx 44$ MPa are around 1.07 to 1.15, those for beams with $f_{cu} \approx 56$ MPa are around 0.94 to 1.22 and those for beams with $f_{cu} \approx 93$ MPa are around 0.91 to 1.22. It may be said, therefore, that the experimental values of ultimate moment generally agree quite closely with the corresponding theoretical values. Thus, the applicability of BS 8110, after modification as suggested by The Concrete Society, to high-strength concrete beams is confirmed.

In most cases, the experimental values of ultimate moment are slightly higher than the corresponding theoretical values. The difference between the experimental and theoretical ultimate moments serves as a kind of strength reserve. For those beams made of concrete with $f_{cu} < 50$ MPa, the experimental values of ultimate moment are always higher than the corresponding theoretical values, leading to an average M_p/M_u ratio of 1.19, which is significantly higher than 1. On the other hand, for those beams with $f_{cu} \approx 56$ MPa, the average M_p/M_u ratio is equal to only about 1.11 and for those beams with $f_{cu} \approx 93$ MPa, the average M_p/M_u ratio is even lower at around 1.02. It appears, therefore, that the amount of such strength reserve varies with the concrete grade and is generally smaller at higher concrete strength.

6.2. Flexural ductility analysis

The ductility of a beam specimen is evaluated in terms of its ductility factor, μ , which is measured from the moment–deflection curve, and the results are listed in the last column of Table 3. It is found that the μ -values obtained are a bit scattered. This is understandable because a small change in the shape of the moment–deflection curve can lead to a relatively large change in the value of μ and hence a small error in the measurement of the moment–deflection curve could produce a significant error in μ . Nevertheless, by statistically correlating the μ -values to the corresponding structural parameters of the beam specimens, the major parameters affecting the ductility of concrete beams can be identified and their effects studied. The μ -values are plotted against the corresponding tension steel ratios, ρ , in Fig. 5. Despite the scattering of the μ -values, an obvious trend

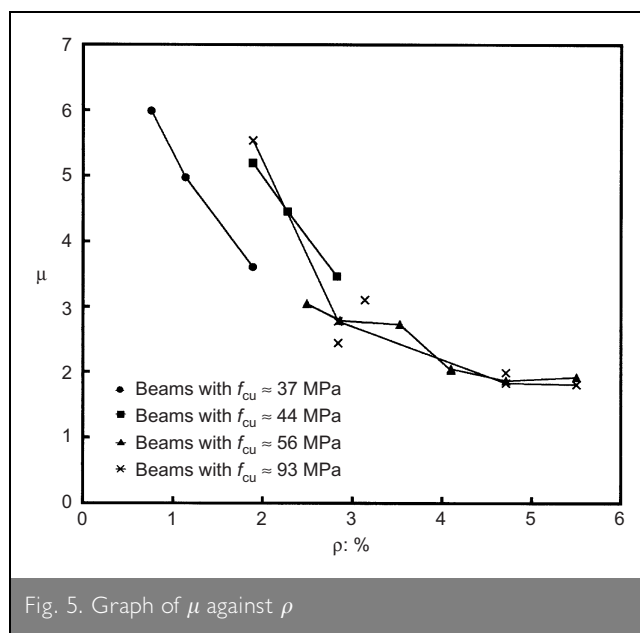


Fig. 5. Graph of μ against ρ

Beam no.	f_{cu} : MPa	ρ : %	ρ_b : %	ρ/ρ_b	M_p : kNm	M_u : kNm	M_p/M_u	μ
1	37.4	0.76	2.04	0.37	77.6	56.0	1.39	5.99
2	36.8	1.14	2.01	0.57	103.5	79.7	1.30	4.97
3	36.4	1.89	1.99	0.95	126.5	114.1	1.11	3.61
4	42.3	1.89	2.55	0.74	129.0	112.0	1.15	5.19
5	46.4	2.28	2.70	0.84	142.8	133.8	1.07	4.45
6	43.2	2.83	2.60	1.09	162.0	144.8	1.12	3.46
7	58.6	2.49	3.57	0.70	164.6	145.7	1.13	3.05
8	57.1	2.86	3.50	0.82	166.2	160.6	1.03	2.79
9	58.6	3.53	3.57	0.99	171.6	183.2	0.94	2.73
10	50.3	4.10	3.12	1.31	197.5	169.7	1.16	2.03
11	58.8	4.10	3.59	1.14	213.5	190.3	1.12	2.05
12	52.9	4.71	3.26	1.44	219.7	179.7	1.22	1.87
13	58.8	5.50	3.58	1.54	239.7	200.3	1.20	1.92
14	95.5	1.89	3.91	0.48	138.0	134.0	1.03	5.54
15	98.0	2.84	3.93	0.72	200.7	191.4	1.05	2.45
16	102.5	2.84	3.94	0.72	181.7	192.4	0.94	2.78
17	87.0	3.14	4.15	0.76	172.0	189.9	0.91	3.11
18	90.3	4.71	3.90	1.21	301.9	247.1	1.22	1.83
19	91.7	4.71	3.93	1.20	253.6	248.6	1.02	1.99
20	83.5	5.50	4.01	1.37	244.7	247.6	0.99	1.81

Table 3. Summary of the test results

showing that the ductility decreases as the tension steel ratio increases is revealed. In any case, for beams made of given materials, the major factor affecting their ductility appears to be the tension steel ratio.

The effect of the tension steel ratio, ρ , on the ductility of a beam is dependent on the properties of the materials used. Since whether the beam is under-reinforced ($\rho/\rho_b < 1$) or over-reinforced ($\rho/\rho_b > 1$) should be more important in determining the ductility of a beam, it is suggested that the μ -values should better be correlated to the tension steel to balanced steel ratios as depicted in Fig. 6. It can be seen from the curves plotted that the reinforced concrete beams made of different grades of concrete lead to different $\mu/(\rho/\rho_b)$ curves. Except for a few anomalous cases, at similar ρ/ρ_b ratios, the ductility factors are generally lower at higher concrete strengths and higher at lower concrete strengths. On the other hand, for a given concrete strength, the ductility factor, μ , is higher when the ρ/ρ_b ratio is small and lower when the ρ/ρ_b ratio is large.

It appears from the above that in general cases, the major structural parameters affecting the ductility of a singly reinforced concrete beam are the tension steel to balanced steel ratio, ρ/ρ_b , and the concrete grade. Assuming that the ductility factor, μ , is a function of ρ/ρ_b and f_{cu} as given by the following equation

$$10 \quad \mu = k(f_{cu})^m(\rho/\rho_b)^n$$

and using regression analysis to determine the values of k , m and n , the correlation equation for estimating μ from ρ/ρ_b and f_{cu} is obtained as

$$11 \quad \mu = 9.5(f_{cu})^{-0.3}(\rho/\rho_b)^{-0.75}$$

The correlation coefficient, R , of the above equation is found to be 0.886. In order to visualise how good the correlation is, the experimental values of μ are plotted against the corresponding

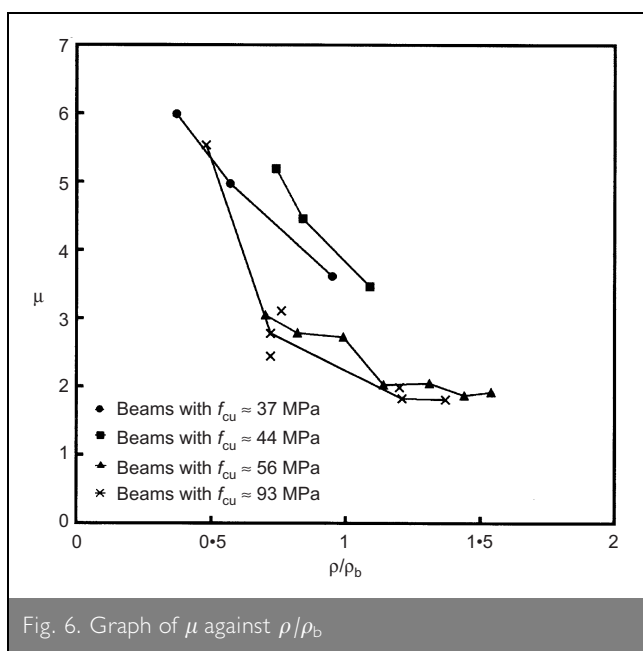


Fig. 6. Graph of μ against ρ/ρ_b

theoretical values in Fig. 7. Although high accuracy cannot be expected, the equation does reveal how the ductility factor, μ , varies with the two parameters ρ/ρ_b and f_{cu} .

To avoid brittle failure and ensure minimum ductility, it is generally considered good practice to limit the tension steel ratio, ρ , to not more than 75% of the balanced steel ratio, ρ_b . Since this practice has been adopted for a long time before the advent of high-strength concrete, this presumably applies mainly to beams made of normal-strength concrete. In order to maintain a similar level of ductility, it is proposed that for beams made of high-strength concrete, the ρ/ρ_b ratio should be limited to a certain maximum value such that the ductility factor of the beam as evaluated by equation (11) is not less than that of a beam with $f_{cu} = 50$ MPa and $\rho/\rho_b = 0.75$. The recommended maximum ρ/ρ_b ratio may be evaluated by

$$12 \quad (f_{cu})^{-0.3}(\rho/\rho_b)^{-0.75} = (50)^{-0.3}(0.75)^{-0.75}$$

which gives

$$13 \quad \rho/\rho_b = 0.75 \times (f_{cu}/50)^{-0.4}$$

For easy reference, the maximum values of ρ/ρ_b for different grades of concrete are tabulated in Table 4.

It can be seen from the values listed that when high-strength concrete is used, the maximum ρ/ρ_b ratio needs to be reduced to avoid brittle failure. Nevertheless, since ρ_b increases with the concrete strength, the maximum value of ρ , which is equal to ρ_b times the maximum ρ/ρ_b ratio, still increases with the concrete strength until $f_{cu} = 80$ MPa. Thus, the use of high-strength concrete in place of normal-strength concrete does allow the use of a slightly higher value of ρ to increase the bending strength of the beam while maintaining similar ductility (see Table 4). For instance, the use of a high-strength concrete with $f_{cu} = 80$ MPa in place of a normal-strength concrete with $f_{cu} = 50$ MPa allows us to increase the tension steel ratio, ρ , from 2.76 to 3.19% which could lead to an

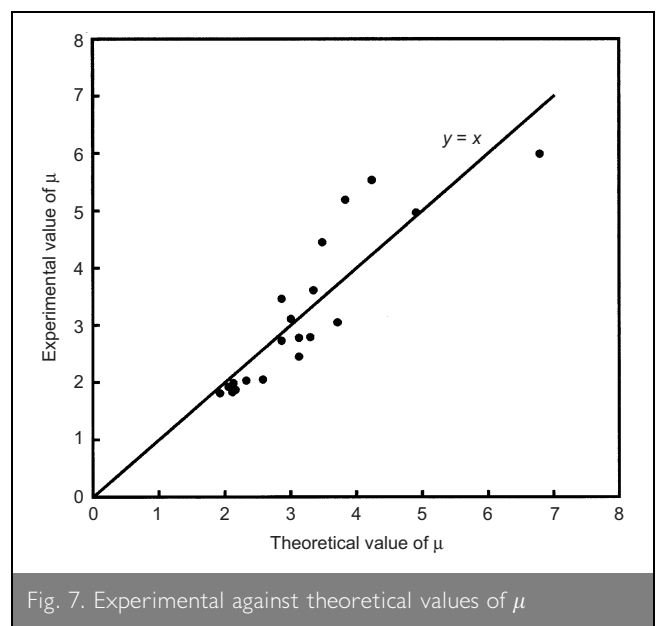


Fig. 7. Experimental against theoretical values of μ

f_{cu} : MPa	ρ_b : %	Max. ρ/ρ_b	Max. ρ : %	Max. $\frac{M_u}{bd^2}$: MPa
40	3.00	0.75	2.25	8.33
50	3.68	0.75	2.76	10.25
60	4.34	0.70	3.04	11.48
70	4.78	0.66	3.15	12.21
80	5.14	0.62	3.19	12.57
90	5.40	0.59	3.19	12.75
100	5.54	0.57	3.16	12.81

Table 4. Maximum values of ρ/ρ_b , ρ and M_u . (Note: ρ_b and M_u are evaluated on the assumption that $f_y = 460$ MPa)

increase in bending strength, M_u , of about 23%. It is only that the net allowable increase in bending strength due to the use of high-strength concrete is not that great (only 23% increase in bending strength even when the concrete strength f_{cu} is increased by 60% from 50 to 80 MPa) and therefore the use of high-strength concrete in reinforced concrete beams may not be a worthwhile pursuit unless there is no better alternative. For high-strength concrete, especially concrete with $f_{cu} > 80$ MPa, to be more useful in beams, its ductility needs to be improved by, say, the provision of confinement or fibre reinforcement.

7. CONCLUSIONS

The flexural strength and ductility of singly reinforced concrete beams made of normal- and high-strength concretes have been studied experimentally. Analysis of the test results leads to the following conclusions.

- The experimental results for flexural strength agree quite closely with the theoretical predictions using the parabolic-rectangular stress block given in British Standard BS 8110 and the ultimate concrete strain recommended by The Concrete Society Technical Report 49, thus verifying the applicability of BS 8110, after modification as per Concrete Society recommendation, to high-strength concrete beams. However, the strength reserve that is normally available when normal-strength concrete is used gradually decreases as the concrete strength increases.
- The major structural parameters determining the flexural ductility of singly reinforced concrete beams are, for given materials, the tension steel ratio and, in general cases, the tension steel to balanced steel ratio and the concrete grade. Based on the available test results and using regression analysis, a simple formula for estimating the flexural ductility of normal- and high-strength concrete beams is developed. This formula, though not expected to be very accurate, can at least serve as a guideline for ductility evaluation and control.
- To avoid brittle failure and ensure minimum ductility, it is proposed to set a maximum limit to the tension steel to balanced steel ratio. The values of the proposed maximum limit, which gradually decreases as the concrete strength increases to account for the lower ductility of higher strength concrete, have been listed in Table 4. Nevertheless, since the balanced steel ratio increases with the concrete

strength, the maximum allowable tension steel ratio still increases with the concrete strength until $f_{cu} = 80$ MPa. Thus, the use of high-strength concrete in place of normal-strength concrete does allow the bending strength of the beam to be increased while maintaining similar ductility. However, the net increase in bending strength due to the use of high-strength concrete is relatively small compared to the increase in concrete strength.

- The further increase in strength of the concrete to be used in reinforced concrete beams beyond the level of $f_{cu} = 80$ MPa offers little advantage when both the strength and ductility of the beams have to be considered. For high-strength concrete with $f_{cu} > 80$ MPa to be more useful in beam structures its ductility needs to be significantly improved.

8. ACKNOWLEDGEMENTS

The authors wish to acknowledge financial support from the Research Grants Council of Hong Kong (Project Reference No. HKU 434/94E) and to express their appreciation to the technical staff in the Structures Laboratory of The University of Hong Kong for their help in conducting the experiment.

REFERENCES

- EUROPEAN COMMITTEE FOR STANDARDIZATION. Eurocode 2: design of concrete structures, part 1-1: general rules and rules for buildings (ENV 1992-1-1). *Concrete Structures Euro-Design Handbook*. Ernst & Sohn Verlag für Architektur und Technische Wissenschaften GmbH, Berlin, 1992.
- ACI COMMITTEE 318. *Building Code Requirements for Structural Concrete (ACI 318M-95) and Commentary (ACI 318RM-95)*. American Concrete Institute, Detroit, 1995.
- FIP-CEB. *High Strength Concrete: State of the Art Report, CEB Bulletin d'Information No. 197, FIP State of the Art Report SR 90/1*. Thomas Telford Ltd, London, 1990.
- ACI COMMITTEE 363. *State-of-the-Art Report on High Strength Concrete, ACI 363R-92*. American Concrete Institute, Detroit, 1992.
- YONG Y. K., NOUR M. and NAWY E. G. Behavior of laterally confined high-strength concrete under axial loads. *Journal of Structural Engineering, ASCE*, 1988, 114, No. 2, 332-350.
- SAATCIOGLU M. and RAZVI S. R. Strength and ductility of confined concrete. *Journal of Structural Engineering, ASCE*, 1992, 118, No. 6, 1590-1607.
- LESLIE K. E., RAJAGOPALAN K. S. and EVERARD N. J. Flexural behavior of high-strength concrete beams. *ACI Journal*, 1976, 73, 517-521.
- SHIN S., GHOSH S. K. and MORENO J. Flexural ductility of ultra-high-strength concrete members. *ACI Structural Journal*, 1989, 86, No. 6, 394-400.
- SARKAR S., ADWAN O. and MUNDAY J. G. L. High strength concrete: an investigation of the flexural behaviour of high strength rc beams. *Structural Engineer*, 1997, 75, No. 7, 115-121.
- PARK R. Ductility evaluation from laboratory and analytical testing. *Proceedings of the 9th World Conference on Earthquake Engineering*, Vol. VIII, Tokyo-Kyoto, 1988, pp. 605-616.

11. WORKING PARTY of THE CONCRETE SOCIETY. *Technical Report No.49: Design Guidance for High Strength Concrete*. The Concrete Society, Slough, UK, 1998.

12. BRITISH STANDARDS INSTITUTION. *Structural Use of Concrete, Code of Practice for Design and Construction*. BSI, London, 1997, BS 8110: Part 1.

Please email, fax or post your discussion contributions to the secretary: email: lyn.richards@ice.org.uk; fax: +44 (0)20 7799 1325; or post to Lyn Richards, Journals Department, Institution of Civil Engineers, 1-7 Great George Street, London SW1P 3AA.